



*Briar Beam of Hollow Bricks and Portland Cement erected at the Exhibition Building, May 1851, by J. B. Wimber and Sons.*

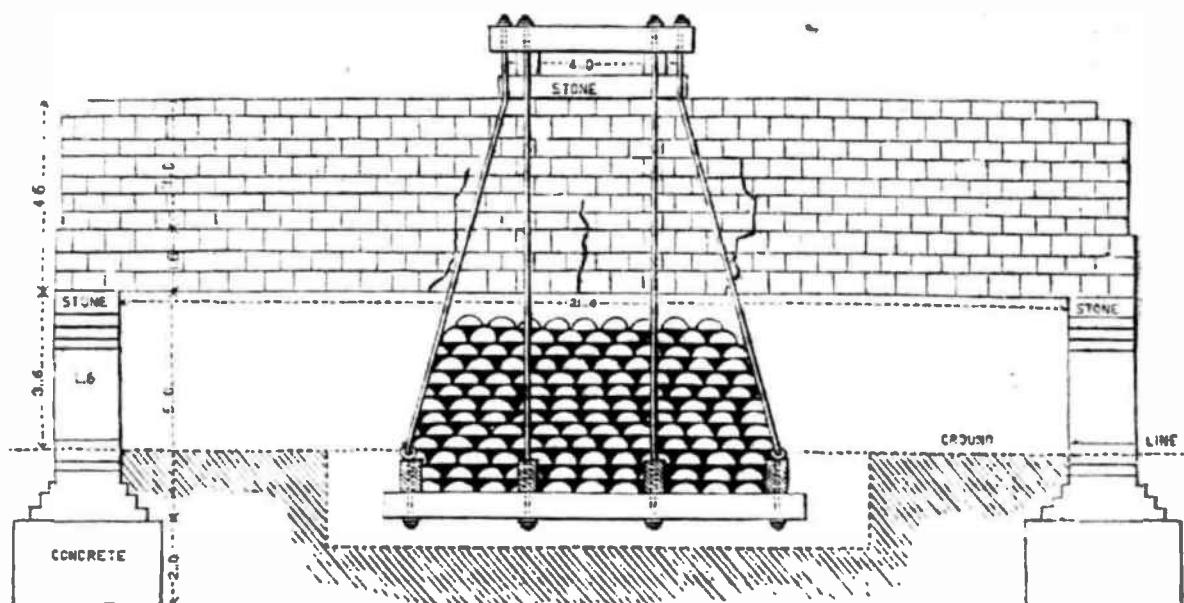

**DIMENSIONS.**  
Neat length . . . . . 24 ft. 4 in.  
" " length . . . . . 21 ft. 4 in. in clear of piers.  
" " depth . . . . . 4 ft. 6 in.  
" " thickness . . . . . 2 ft. 3 in. bottom, and 1 ft. 6 in. upper part.  
*Built of equal parts cement and sand; completed, 12th April; centres struck, 22nd April.*

**CONSUMED:**  
1,200 hollow bricks, weight . . . 10,750 lbs.  
32 bushels cement } 6,400 ..  
32 ditto sand } —————— 17,150 lbs.  
  
If built in common bricks would require—  
2,710 stuck bricks, weight . . . 13,420  
50 bushels cement } 8,000 21,420  
50 ditto sand } difference 4,270 lbs.  
  
Weight of scale and iron work . . . 1,722 lbs.  
" of stone . . . . . 672 ..  
" of beam in suspension } 15,000  
between piers . . . . . —————— 17,464 lbs.  
  
In common bricks:  
Scale and stone . . . . . 2,464  
Net weight of beam . . . . . 18,743 21,207 lbs.  
difference 3,743 lbs. = 1 ton. 13 cwt. 19 gr. lbs.

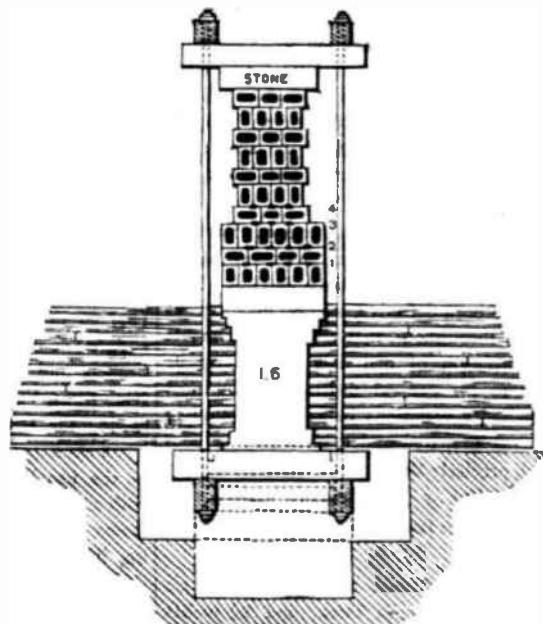

Roman cement in the ratio of 2:124 to 1, or, subject with conditions that are extraneous to in round numbers, 24 to 1. This reasoning, the immediate inquiry,<sup>\*</sup> however, is scarcely correct, since it does not take sufficiently into consideration the strength in this experiment must not be overlooked. dependent on disposition of the material.

From some experiments made upon Portland and Roman cement, where solid bricks were used with each, the superiority of Portland cement was found to be much greater than this is shewn by experiment,—but when we consider the nature of the structure, and take into account the circumstance of the Roman cement beam having been built seventeen months before the breaking weight was applied, whereas the Portland cement beam had been only erected five months, we are not surprised that the experiment with the hollow bricks did not exhibit the full strength of the Portland cement. It is to be regretted that hollow bricks were used, as it would have been better to have rested the comparison upon two beams as strictly analogous as possible, instead of complicating the

The tensile strength of wrought iron per square inch of section, may be called 27 tons. The mean of Mr. Telford's experiments gave 29 tons, as did some conducted under our own superintendence. Mr. G. Rennie says 24.93, and Capt. Brown 25 tons.<sup>†</sup>

In the hollow-brick beam there were fifteen pieces of hoop iron bond, one-and-a-half inch by one-sixteenth of an inch, nearly; namely, four in the first course, four in the second, three in the third, and two in each of the next.<sup>†</sup> The pieces of iron were all broken, except one in the bottom course, one in the second, and one in the top course.

This very interesting proceeding suggests many observations, but we must now pass on to the experiments, also on Portland cement, which were exhibited on the same occasion by Messrs. Robins and Aspdin, of Scotland-yard.

\* Eight or nine tons may be considered a safe load.

† In the diagram, by mistake, only fourteen are shown.

Hollow bricks are usually better moulded and more thoroughly burnt than ordinary stocks.